JBP
Journal of Biochemicals and Phytomedicine
eISSN: 2958-8561

Green Synthesis, Characterization, and *In Vivo* Anti-Plasmodial Activity of Copper Oxide Nanoparticles Using *Moringa oleifera* Leaf Extract

Olutayo Olawumi Olajide [1]*, Stella Adedunni Emmanuel [2], Omotola Michael Fayomi [3]

[1] Chemistry Advanced Research Centre, Sheda Science and Technology Complex (SHESTCO), Abuja, Nigeria
[2] Chemistry Department, National Open University of Nigeria, Abuja Headquarters, Nigeria
[3] Department of Chemistry, Joseph Sarwuan Tarka University, Makurdi, Nigeria

ARTICLE INFO

Article Type:
Research

Article History:
Received: 16 Feb 2025
Revised: 19 May 2025
Accepted: 25 May 2025
Available online: 30 Jun 2025

Keywords:
Copper Oxide Nanoparticles,
Moringa,
SEM,
XRD,
Plasmodial activity

* *Corresponding author:*
E-mail: olajidewumi@rocketmail.com

ABSTRACT

Introduction: Green synthesis is a commonly used method in the preparation of metal nanoparticles due to its cost-effectiveness and environmentally friendly nature. Metal nanomaterials have demonstrated superior inhibitory properties compared to their corresponding biological extracts. In this study, *Moringa oleifera*-based copper oxide nanoparticles designated (CuONPMOLE) were synthesized using *Moringa oleifera* (MOLE) leaf extract and tested for their antiplasmodial effects in an *in vivo* model.
Methods: The biosynthesized cuprite nanoparticles were characterized via UV-vis absorption spectroscopy, Fourier transform infrared spectroscopy (FT-IR), scanning electron microscopy (SEM), energy-dispersive spectroscopy (EDX), and X-ray diffraction (XRD). Inhibitory activity of CuONPMOLE on *Plasmodium berghei* was evaluated in rats.
Results: The results from SEM showed the morphology of CuONPMOLE, which appeared predominantly spherical, with some hollow areas. EDX analysis confirmed the presence of Cu atoms at 85.87%. The copper nanoparticles exhibited crystalline properties with an average size of 20.34 nm, and the XRD pattern displayed characteristic peaks corresponding to (111) and (200) reflections of the cubic cuprite crystal. The action CuONPMOLE against *Plasmodium berghei* parasites resulted in inhibitory activity of 43.37 ± 2.46%, demonstrating promising antiplasmodial activity and a notable decrease in malaria parasite growth ($P<0.05$).
Conclusion: The effectiveness of CuONPMOLE could be attributed to the plant phytochemicals present along with copper ions.

Please cite this paper as:
Olajide OO, Emmanuel SA, Fayomi OM. Green synthesis, characterization, and in vivo anti-plasmodial activity of copper oxide nanoparticles using *Moringa oleifera* leaf extract. Journal of Biochemicals and Phytomedicine. 2025; 4(1): 31-39. doi: 10.34172/jbp.2025.5.

Introduction

Bioactive compounds present in plant and spice extracts play a vital role due to their active functional groups, such as hydroxyl, aldehyde, amine, and carboxyl units, which are instrumental in reducing and stabilizing metals (Patra and El Kurdi, 2021). Conversely, the use of plant extracts for biogenic synthesis, exemplified by *Moringa oleifera*, has garnered attention as an environmentally friendly and cost-effective method with potential applications in drug delivery and antimicrobial treatments (Pagar et al., 2020). *M. oleifera* is renowned for its rich content of bioactive compounds, including flavonoids, polyphenols, alkaloids, and vitamins, making it a noteworthy source for reducing and capping agents in the synthesis of metal nanoparticles (Aaga and Anshebo, 2023). The bioactive elements within *M. oleifera* play a pivotal role in various pharmacological activities, highlighting its promise for sustainable synthetic metal nanoparticles (Bhalla et al., 2023; Ibrahim et al., 2021).

Copper oxide nanoparticles exhibit distinctive antimicrobial and antiparasitic properties, showing promise in combatting malaria parasites (Jayaseelan et al., 2022). However, traditional chemical synthesis approaches for copper oxide nanoparticles often necessitate high-temperature reducing and stabilizing agents, posing environmental hazards (Itodo et al., 2018). Malaria, stemming from Plasmodium parasites transmitted via Anopheles mosquito bites, remains a significant global health issue, particularly affecting tropical regions (Sukkanon et al., 2022). Annually, malaria claims around 409,000 lives, with a notably high mortality rate among infants and pregnant women (Monroe et al., 2022). Beyond the loss of life and health implications, malaria imposes a substantial socioeconomic burden due to healthcare costs, decreased productivity, and barriers to education and development, necessitating innovative interventions (Ahuru et al., 2021).

Therefore, leveraging at the properties of nanoparticles emerges as a promising strategy for diverse medical applications, notably in drug delivery (Qiu et al., 2023), imaging (Guan et al., 2023), and cancer therapy (Ghaffarlou et al., 2023). Nanoparticles offer enhanced drug loading and targeted delivery in malaria treatment, improving therapeutic effectiveness (Ghosh & Banerjee, 2020). Their capacity to enhance anti-malarial drugs ensures sustained efficacy and improved bioavailability (Kannan et al., 2019), underscoring their potential in malaria treatment for enhanced efficiency and delivery. We have previously reported the results of the activities of the nanoparticle of copper oxide with extracts of the roots and stem bark of MO (Emmanuel et al., 2025), this study therefore provides further insight to the properties of the copper oxide nanoparticles utilizing Moringa oleifera leaf extract to evaluate their anti-plasmodial potential in an in vivo model.

Materials and Methods

M. oleifera Leaf Extract (MOLE) Preparation

A fresh extract of *M. oleifera* was prepared using freshly harvested leaves sourced from the *M. oleifera* plantation at the Sheda Science and Technology Complex (SHESTCO) in Abuja, where herbarium voucher was deposited. The leaves were thoroughly cleaned with distilled water to eliminate impurities before being air-dried. To prepare the extract, 6 grams of finely powdered *M. oleifera* leaf were added to 200 mL of deionized water. The mixture was then heated to 100°C between duration of 20 to 30 minutes. Subsequently, the obtained extract was filtered using Whatman No. 1 filter paper and was stored at 4°C for future use.

Synthesis of CuONPMOLE

Initially, 3.63 grams of copper acetate (0.02M) were dissolved in 70 mL of deionized water and agitated using a magnetic stirrer for 10 minutes at room temperature. Subsequently, 30 mL of *M. oleifera* leaf extract (with a pH value of 7.5) were added drop by drop and heated to 60°C with continuous stirring at 250 rpm for 3 hours. The resulting solution underwent centrifugation at 3000 rpm for 20 minutes, followed by washing the precipitates with ethanol to eliminate impurities. The washed precipitates were then dried in an oven at 90°C for 2 hours until the solvent evaporated, and subsequently calcined in a preheated muffle furnace at 400 $\pm$10°C, resulting in the formation of brown CuONPs. (Almisbah and Mohammed, 2023).

Characterization of CuONPMOLE

The synthesis of CuONPMOLE was characterized using the JENWAY 6405 UV-Vis spectrophotometer. The UV-Vis absorption spectrum of copper oxide was characterized by conducting a wavelength scan ranging from 200 to 800 nm. The absorption spectra of the synthesized copper oxide nanoparticles obtained was generated and deduced. Following this, the FT-IR spectra of CuONPMOLE were analysed using an Agilent 630 Cary FT-IR Spectrophotometer. This instrument features an ATR module for liquids and solids, as well as a 'Dial Path' module for absorbance spectra of liquids, films, and gels. The CuONPMOLE were examined on KBr discs with a 4% (w/w) solid/KBr mixture, and the FT-IR spectra were recorded within the range of 400–4,000 cm-1. This analysis facilitated the study of bond details within compounds and the investigation of biomolecules present in plant extracts using 1 mm thick re-crystallized KBr discs.

For X-ray diffraction analysis, the Thermo Scientific ARL 'XTRA X-ray diffractometer with serial number

197492086 was employed at Umaru Musa Yar'adua University in Katsina State, Nigeria. XRD is a non-destructive technique used to characterize crystalline materials, providing valuable insights into structures, phases, texture, lattice parameters, chemical composition, and various structural parameters like average grain size, crystallinity, strain, and crystal defects.

Additionally, the PRO: X: 800-07334 Phenom World EDX Scanning Electron Microscope with serial number MVE01570775 was utilized to examine the surface morphology of materials. This instrument offers detailed information on structures and can conduct pore, fibre metric, and particle size analyses for nanoparticle materials.

Experimental Animals

The experimental Wistar rats were sourced from the College of Veterinary Medicine at Joseph Sarwuan Tarka University in Makurdi. Each group of experimental rats was housed in a 15x30cm cage with metal tops, which underwent regular thorough cleaning. Bedding materials, specifically wood shavings (sawdust), were utilised and replaced every week.

In vivo Parasitaemia Infection Assessment

The effectiveness of synthesized copper oxide nanoparticles was evaluated along with *M. oleifera* leaf extract, serving as the capping agent, following a methodology previously documented by researchers (Gitau et al., 2023).

After acclimating, Wistar rats weighing between 115 – 120 g for a period of 2 weeks, they were randomly segregated into four groups, with two rats in each group. Groups 1 and 2 were allocated as the test groups, while Groups 3 and 4 were assigned as the positive and negative control groups, respectively. Group 1 received treatment with CuONPMOLE, and Group 2 with the *M. oleifera* leaf extract. Group 3 was administered the standard drug Artemether as a positive control, while Group 4, as the negative control, received no treatment.

Approximately 2 mL of blood was freshly drawn from the Wistar rats and combined with 0.6 mL of normal saline. The rats were induced with 0.5 mL of parasitaemia (1 x 107 *Plasmodium berghei*) intraperitoneally to initiate infection. Subsequently, the rats were monitored for 24 hours to allow the Plasmodium parasite to propagate.

Following the 24-hour incubation period, the test groups were treated with the *M. oleifera* leaf extract and copper oxide nanoparticles, as well as the positive control (Artemether), each administered at a single dose of 50 mg/kg body weight and left for 48 hours. After this interval, blood samples were collected from a pricked tail and smeared onto a clean glass slide to create a thin blood film. The sample was air-dried in the laboratory for an hour, mixed with methanol, stained with Giemsa stain for 10 minutes, rinsed, dried, and examined under a microscope using a x100 objective lens. The percentage parasitemia and percentage inhibition on the red blood cells (RBC) were calculated using the equations (1) and (2) as follows:

(1)

$$\% \text{ Parasitaemia} = \frac{Number\ of\ Parasitized\ Cells\ x\ 100}{Number\ of\ Red\ Blood\ Cells\ (RBC)}$$

(2)

$$\% \text{ Inhibition} = \frac{\% Parasitaemia_{control} - \% Parasitaemia_{test\ group}\ x\ 100}{\% Parasitaemia_{control}}$$

Statistical Analysis

The data were analysed utilizing OriginPro Software® 2017. The study results were presented as the mean ± standard error of the mean (M±SEM). One-way analysis of variance (ANOVA) was employed to compare the treatment groups, supplemented by Tukey and Levene post-hoc analyses. Statistical significance was determined at a threshold of $p < 0.05$.

Results

UV–Vis analysis

The result of the UV-Vis analysis, depicted graphically in Figure 1, confirm the synthesis of CuONPMOLE.

FT-IR Analysis

The FTIR spectrum analysis of copper oxide nanoparticles further supports with the appearance of some distinct peaks (Figure 2), notably at 813 cm-1, attributed to metal-oxygen (Cu-O) stretching vibrations, aligning with the anticipated copper oxide composition.

SEM Analysis of CuONPMOLE

The surface morphology and size of CuONPMOLE was scrutinized through SEM analysis. The SEM illustrations depicting the images showcased intriguing visual representations, as shown in Figures 3(a) and (b) at magnifications of 5 µm and 1 µm, respectively.

EDX Analysis of CuONPMOLE

To verify the presence of the metals in CuONPMOLE, an EDX analysis was conducted, revealing distinctive peaks displayed in Figure 4 and the constituents in Table 1.

XRD Pattern of CuONPMOLE

The powder X-ray diffraction (XRD) pattern of CuONPMOLE is illustrated in Table 2 and Figure 5, displaying diffraction peaks identifiable with the cubic phase of Copper (I) oxide crystals (JCPDS card No. 01-078-2076).

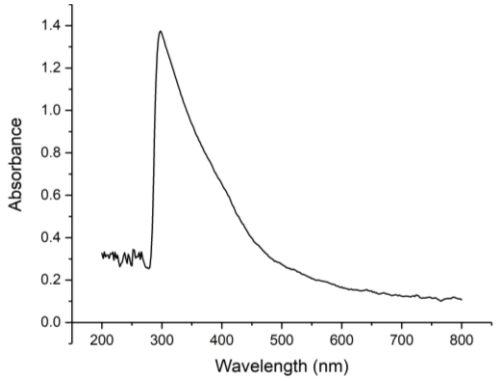

Figure 1: UV-visible spectra of CuONPMOLE
CuONPMOLE*: Moringa oleifera*-based copper oxide nanoparticles designated (CuONPMOLE) synthesized using *Moringa oleifera* (MOLE) leaf extract

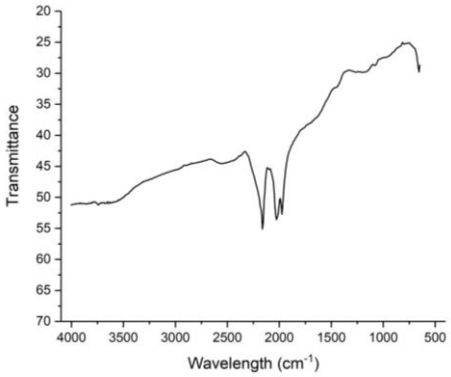

Figure 2: FTIR spectrum analysis of CuONPMOLE

CuONPMOLE*: Moringa oleifera*-based copper oxide nanoparticles designated (CuONPMOLE) synthesized using *Moringa oleifera* (MOLE) leaf extract

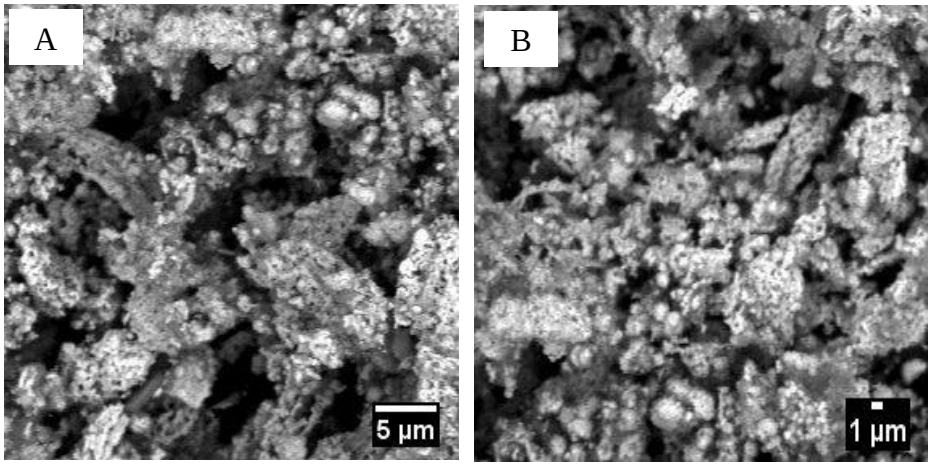

Figure 3: SEM of CuONPMOLE.
CuONPMOLE*: Moringa oleifera*-based copper oxide nanoparticles designated (CuONPMOLE) synthesized using *Moringa oleifera* (MOLE) leaf extract; A: 5 µm; B: 1 µm.

Table 1. EDX weight ratio of electrospun cuonps derived from *Moringa oleifera* leaf extract

Element Number	Element Symbol	Element Name	Atomic Concentration	Weight Concentration
29	Cu	Copper	85.87	93.59
11	Na	Sodium	8.90	3.51
19	K	Potassium	0.98	0.66
13	Al	Aluminum	1.18	0.55

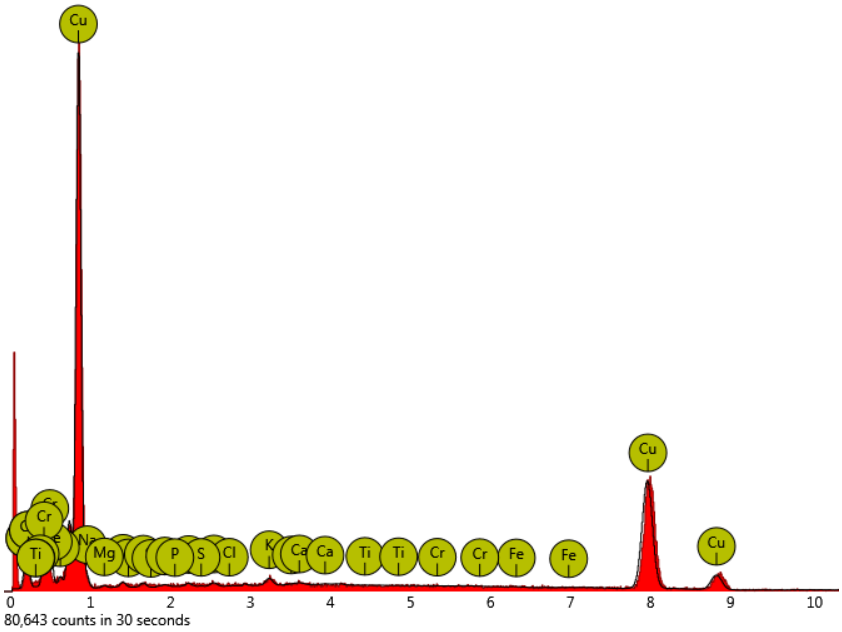

Figure 4: EDX spectrum analysis of CuONPMOLE.
CuONPMOLE*: Moringa oleifera*-based copper oxide nanoparticles designated (CuONPMOLE) synthesized using *Moringa oleifera* (MOLE) leaf extract.

Table 2. Some crystallographic parameters of the synthesized CuONPMOLE based on the x-ray diffraction pattern

S/N	Peak Position (2θ)	FWHW (β) (degree)	Crystallite size D (nm)	D (Average) (nm)
1	29.74	0.5925	13.88	20.34
2	32.88	0.6000	13.81	
3	36.54	0.3937	21.25	
4	39.06	0.3402	24.78	
5	42.38	0.5745	14.84	
6	43.40	0.2874	29.76	
7	45.30	0.3349	25.71	
8	50.58	0.3374	26.04	
9	61.44	0.7122	12.98	

CuONPMOLE*: Moringa oleifera*-based copper oxide nanoparticles designated (CuONPMOLE) synthesized using *Moringa oleifera* (MOLE) leaf extract.

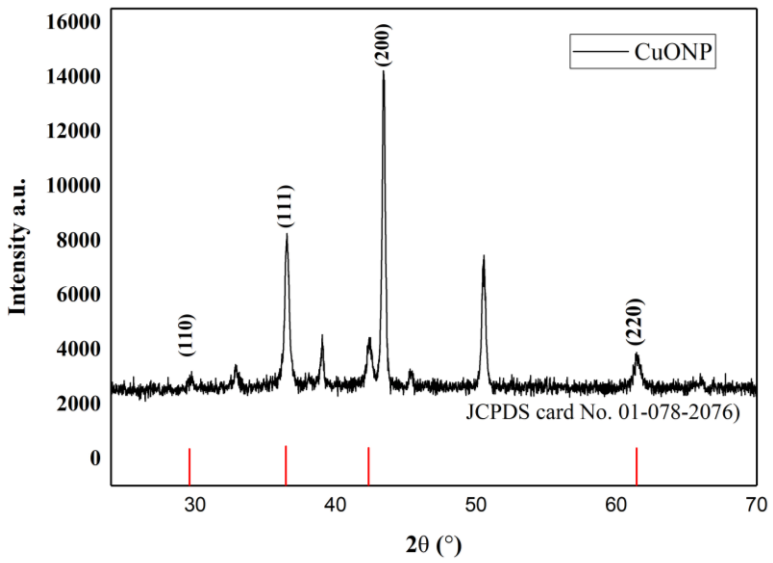

Figure 5: XRD patterns for synthesized CuONPMOLE.
CuONPMOLE*: Moringa oleifera*-based copper oxide nanoparticles designated (CuONPMOLE) synthesized using *Moringa oleifera* (MOLE) leaf extract; Different peak positions at 2θ along with the JCPDS card number indicating the miller indices of the synthesized nanoparticles.

Antiplasmodial Evaluation of CuONPMOLE

The efficacy of CuONPMOLE was compared with the crude MOLE and a positive control (Artemether) in combatting *Plasmodium* parasites. Figure 6 illustrates the average parasitized cells in the negative control and test groups among the experimental rats, with values presented as mean and standard error of the mean, with significance set at $p<0.05$ for comparison.

The in vivo anti-plasmodial potential, gauged by percentage inhibition, showed that the test materials (CuONPMOLE and MOLE) exhibited moderate activity against the growth of *Plasmodium berghei*. CuONPMOLE demonstrated significant inhibition of parasitaemia at 43.37±2.46%, while the MOLE showed inhibition at 13.33±7.88%. Artemether exhibited a percentage inhibition of 70.45±0.01%.

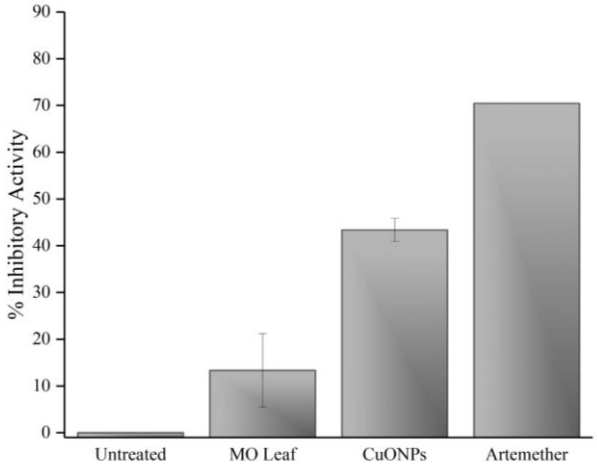

Figure 6: *In vivo* anti-plasmodial activity of CuONPMOLE
CuONPMOLE*: Moringa oleifera*-based copper oxide nanoparticles designated (CuONPMOLE) synthesized using *Moringa oleifera* (MOLE) leaf extract; Artemether (positive control); Values are presented as mean±SEM; $p<0.05$ was considered significant for comparison.

DISCUSSION

Previous reports of similar works underscored the potential of air-dried plants in acting as a stabilizing and reducing agent for generating metal nanoparticles (Teklu et al., 2023) as well as highlights on the initial color alteration observed during synthesis which could be attributed to the reaction between a plant extract and a metal solution. Moreover, distinct spectra indicative of shifts in electronic energy levels were reported.

CuONPMOLE was analyzed using UV–vis spectrophotometry ranging between 200 to 800 nm. The result of the UV-Vis analysis evidenced by an absorption band present around 300 nm wavelength, aligning with recent research outcomes (Nzilu et al., 2023).

The absorption bands from the FTIR spectra in Figure 2 further showed, the peak at 1334 cm-1 as stretching vibrations associated with alcohol deformation. Additionally, the peak observed at 2117 cm-1 indicates stretching in C≡N, potentially linked to nitrile functionality (Junejo et al., 2023). The peak at 2325 cm-1 likely signifies a metal-carbonyl (C=O) stretching vibration, suggesting the presence of carbonyl ligands on the nanoparticles' surface. Moreover, the peak at 2653 cm-1 is attributed to aryl C-H stretching vibrations. Notably, a prominent broad band at 3779 cm-1 indicates O-H stretching vibrations from surface hydroxyl groups or adsorbed water molecules (Akpomie and Conradie, 2023). These findings collectively offer valuable insights into the composition and surface properties of copper oxide nanoparticles, crucial for understanding their potential biological applications. Moreover, qualitative phytochemical screenings of the leaf extract in the previous works have indicated various phytochemical constituents such as phenols, aromatic compounds, carboxylic acids, alcohols, saponins, alkaloids, and flavonoids (Oladeji et. al, 2019; Walid et.al, 2023; Obialo et.al, 2024).

The presence of shifting peaks in the CuONPs following reduction with $Cu(COOCH3)_2$ suggests interactions between functional groups present in the plant extract and the copper salt precursor. This interaction plays a pivotal role in the reduction and stabilization of CuONPs.

The SEM images in both figures 3 (a) and (b) clearly showed rough surfaces of the CuONPMOLE exhibiting a predominantly spherical shape with dispersed hollows of varying sizes (Singh et al., 2019). This observation suggests the encapsulation of the metal with bioactive compounds sourced from plants, encompassing carotenoids, fatty acids, carbohydrates, polyphenols, amino acids, and vitamins (Waris et al., 2021).

The EDX spectrum derived along with the SEM images confirms the synthesis of copper nanostructures. Specifically, the copper content was quantified at 85.87 within the spectrum. Furthermore, Table 2 provides details on the full width at half maximum (FWHM, β), crystallite size (D), and associated parameters. The crystallite size, which represents the coherent diffraction volume of a material, is a critical parameter. For powdered materials, it may correspond to grain size, while in polycrystalline thin films, it can reflect thickness.

Peak broadening in the XRD pattern, observed at different 2θ positions along with the JCPDS card number, indicates the Miller indices of the synthesized nanoparticles. This broadening suggests the presence of small nanocrystals (Bin et al., 2022). As detailed in Table 2, the crystallite sizes range from 12.98 nm to 29.76 nm, with an average size of 20.34 nm. The peak positions at 2θ values of 29.74°, 36.54°, 42.38°, and 61.44° correspond to the (110), (111), (200), and (220) crystal planes, respectively (Kirfel & Eichhorn, 1990).

The in vivo antiplasmodial potential aligns with recent research findings, supporting the inhibitory effects of metal nanomaterials on malarial parasite proliferation (Veeragoni et al., 2023; Adeyemi et al., 2018).

We can further state that the anti-plasmodial efficacy of CuONPMOLE nanoparticles is linked to the phytochemicals present in *M. oleifera* leaf extract, known for enhancing immune function. Once introduced into infected red blood cells, CuONPMOLE nanoparticles can liberate copper (I) ions, inducing heightened oxidative stress within the cell, ultimately leading to parasitic nucleus damage. This evaluation of cuprite nanoparticles derived from plant sources signifies a promising avenue for potential antimalarial agents (Gitau et al., 2023).

Conclusion

The investigation outlines a cost-effective and environmentally friendly approach for synthesizing the copper oxide nanoparticles CuONPMOLE. Various characterization techniques, including UV-VIS, FTIR, SEM, EDX, and XRD, were utilized to confirm the properties of the metal nanoparticles. CuONPMOLE exhibited significant antiplasmodial efficacy against *P. berghei* in in vivo models, surpassing the effects of *M. oleifera* leaf extract. This enhanced antiplasmodial activity of CuONPMOLE is attributed to the presence of metabolites within the *M. oleifera* leaf extract. Furthermore, CuONPMOLE were observed to inhibit parasitaemia growth in an in vivo rat model infected with *P. berghei.*

Declaration

Conflict of interest

There is no conflict of interest among the authors.

Acknowledgement

None.

Consent for publications

The authors gave approval for the publication of the manuscript.

Funding/support

None.

Authors' contributions

Conceptualization, data curation, formal analysis, funding acquisition, investigation , methodology, project administration, resources, software, supervision, validation, visualization, writing–original draft: Olajide Olutayo Olawumi
Writing–review & editing, conceptualization, funding acquisition, methodology, supervision, validation, and resources.
Fayomi Omotola Michael: Conceptualization, visualization, writing-original draft, data curation, software, investigation, methodology, supervision, and resources : Stella Adedunni Emmanuel:

Ethical considerations

All ethical issues (including plagiarism, misconduct, data fabrication, falsification, double publication, or redundancy) have been thoroughly observed by the author.

References

Aaga GF, Anshebo ST. Green synthesis of highly efficient and stable copper oxide nanoparticles using an aqueous seed extract of *Moringa stenopetala* for sunlight-assisted catalytic degradation of Congo red and alizarin reds. Heliyon. 2023; 9(5): e16067. doi: 10.1016/j.heliyon.2023.e16067.

Adeyemi OS, Molefe NI, Awakan J, Nwonuma CO, Oluwaseyi O, Olaolu T, et al. Metal nanoparticles restrict the growth of protozoan parasites. Artificial Cells, Nanomedicine, and Biotechnology. 2018; 46(S3): S86–94. doi: 10.1080/21691401.2018.1489267.

Ahuru BRR, Okungbowa OG, Iseghohi JO, Akpojubaro EH. Non-utilization of primary healthcare centres for skilled pregnancy care among women in rural communities in delta state, southern nigeria: perspectives from mothers, fathers, and healthcare providers. Journal of International Women's Studies. 2021; 22(9): 142–159.

Akpomie KG, Conradie J. Efficient adsorptive removal of paracetamol and thiazolyl blue from polluted water onto biosynthesized copper oxide nanoparticles. Scientific Reports. 2023; 1–15. doi: 10.1038/s41598-023-28122-0.

Almisbah SRE, Mohammed AMA. Green synthesis of CuO nanoparticles using *Hibiscus sabdariffa* L . extract to treat wastewater in Soba Sewage Treatment Plant , Sudan. 2023; 87(12): 3059–71. doi: 10.2166/wst.2023.153.

Bhalla N, Ingle N, Jayaprakash A, Patel H, Patri SV, Haranath D. Green approach to synthesize nano zinc oxide via Moringa oleifera leaves for enhanced anti-oxidant, anti-acne and anti-bacterial properties for health & wellness applications. Arabian Journal of Chemistry. 2023; 16(3): 104506. doi: 10.1016/j.arabjc.2022.104506.

Bin M, Hossain S, Chowdhury F, Ahmed S. Synthesis and characterization of CuO nanoparticles utilizing waste fish scale and exploitation of XRD peak profile analysis for approximating the structural parameters. Arabian Journal of Chemistry. 2022; 15(10): 104117. doi: 10.1016/j.arabjc.2022.104117.

Ghaffarlou M, Mohammadi A, Mousazadeh N, Salehiabar M, Kalantari Y, Charmi J, Barsbay M, Ertas YN, Danafar H, Rezaeejam H, Nosrati H, Javani S. Facile preparation of silver based radiosensitizers via biomineralization method for enhanced in vivo breast cancer radiotherapy. Scientific Reports. 2023; 13(1): 1–12. doi: 10.1038/s41598-023-40763-9.

Ghosh A, Banerjee T. Nanotized curcumin-benzothiophene conjugate: A potential combination for treatment of cerebral malaria. IUBMB Life,. 2020; 72(12): 2637–50. doi: 10.1002/iub.2394.

Gitau W Edinah, Kwamboka Songoro Jeremiah, Waweru Gathirwa Francis K, Kariuki HN. In vivo antiplasmodial activities of stem bark extracts of Avicennia marina in Plasmodium berghei -infected mice. Pan African Medical Journal. 2023; 44(93): 1–19.

Guan X, Zhang L, Lai S, Zhang J, Wei J, Wang K, Zhang W, Li C, Tong J, Lei Z. Green synthesis of glyco-CuInS2 QDs with visible/NIR dual emission for 3D multicellular tumor spheroid and in vivo imaging. Journal of Nanobiotechnology. 2023; 21(1): 1–20. doi: 10.1186/s12951-023-01859-6.

Ibrahim AM, Mohamed, F, Al-Quraishy S, Abdel-Baki AAS, Abdel-Tawab H. Green synthesis of Cerium oxide / Moringa oleifera seed extract nano-composite and its molluscicidsal activities against biomophalaria alexanderina. Journal of King Saud University - Science. 2021; 33(3): 101368. doi: 10.1016/j.jksus.2021.101368.

Itodo AU, Itodo OM, Iornumbe E, Fayomi MO. Sorptive chelation of metals by inorganic functionalized organic WOx-EDA nanowires: adsorbent characterization and isotherm studies. Progress in Chemical and Biochemical Research. 2018; 1 (1): 50-9.

Jayaseelan C, Abdulhaq A, Ragavendran C, Mohan, S. Phytoconstituents Assisted Biofabrication of Copper Oxide Nanoparticles and Their Antiplasmodial, and Antilarval Efficacy: A Novel Approach for the Control of Parasites. Molecules. 2022; 27(23): doi: 10.3390/molecules27238269.

Junejo F, Aziz A, Abbas A, Zehra KE, Bhutto AA, Ahmed T, Rehman AU. Ecological fabrication of copper oxide nanoparticles for enhanced photocatalytic degradation of methylene blue and rhodamine B. Dye. Inorganic Chemistry Communications. 2023; 158(P1): 111547. doi: 10.1016/j.inoche.2023.111547.

Kannan D, Yadav N, Ahmad S, Namdev P, Bhattacharjee S, Lochab B, Singh S. Pre-clinical study of iron oxide nanoparticles fortified artesunate for efficient targeting of malarial parasite. EBioMedicine. 2019; 45: 261–277. doi: 10.1016/j.ebiom.2019.06.026.

Kirfel A, Eichhorn K. Accurate structure analysis with synchrotron radiation. The electron density in Al2O3 and Cu2O. Acta Crystallographica Section A. 1990; 46(4): 271–284. doi: 10.1107/S0108767389012596.

Monroe A, Williams NA, Ogoma S, Karema C, Okumu F. Reflections on the 2021 World Malaria Report and the future of malaria control. Malaria Journal. 2022; 21(1): 1–6. doi: 10.1186/s12936-022-04178-7.

Nzilu DM, Madivoli ES., Makhanu DS, Wanakai SI, Kiprono GK, Kareru PG. Green synthesis of copper oxide nanoparticles and its efficiency in degradation of rifampicin antibiotic. Scientific Reports. 2023; 13(1): 1–18. doi: 10.1038/s41598-023-41119-z.

Pagar K, Ghotekar S, Pagar T, Nikam A, Pansambal S, Oza R, et al. Antifungal activity of biosynthesized CuO nanoparticles using leaves extract of *Moringa oleifera* and their structural characterizations. Asian Journal of Nanoscience and Materials. 2020; 3(1): 15–23. doi: 10.26655/AJNANOMAT.2020.1.2.

Patra D, El Kurdi R. Curcumin as a novel reducing and stabilizing agent for the green synthesis of metallic nanoparticles. Green Chemistry Letters and Reviews. 2021; 14(3): 474–47. doi: 10.1080/17518253.2021.1941306.

Qiu L, Shen R, Wei L, Xu S, Xia W, Hou Y, et al. Designing a microbial fermentation-functionalized alginate microsphere for targeted release of 5-ASA using nano dietary fiber carrier for inflammatory bowel disease treatment. Journal of Nanobiotechnology. 2023; 21(1): 1–19. doi: 10.1186/s12951-023-02097-6.

Selvaraj SP. Enhanced surface morphology of copper oxide (CuO) nanoparticles and its antibacterial activities. Materials Today: Proceedings. 2022; 50(7): 2865–8. doi: 10.1016/j.matpr.2020.09.574.

Singh J, Kumar V, Kim K. Rawat M. Biogenic synthesis of copper oxide nanoparticles using plant extract and its prodigious potential for photocatalytic degradation of dyes. Environmental Research. 2019; 177(May): 108569. doi: 10.1016/j.envres.2019.108569.

Sukkanon C, Masangkay FR, Mala W, Kotepui KU, Wilairatana P, Chareonviriyaphap T, et al. Prevalence of *Plasmodium spp*. in Anopheles mosquitoes in Thailand: a systematic review and meta-analysis. Parasites and Vectors. 2022; 15(1): 1–18. doi: 10.1186/s13071-022-05397-2.

Teklu B, Kadiri SK, Vidavalur S. Green synthesis of copper oxide nanoparticles using Balanites aegyptiaca stem bark extract and investigation of antibacterial activity. Results in Chemistry. 2023; 6(October): 101152. doi: 10.1016/j.rechem.2023.101152.

Waris A, Din M, Ali A, Ali M, Afridi S, Baset A. A comprehensive review of green synthesis of copper oxide nanoparticles and their diverse biomedical applications. Inorganic Chemistry Communications. 2021; 123 (November 2020): 108369. doi: 10.1016/j.inoche.2020.108369.

Copyright © 2024 The Author(s). This is an open-access article distributed under the terms of the Creative Commons Attribution License (http://creativecommons.org/licenses/by/4.0), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.